

Electronic structure of superconducting graphite intercalate compounds: The role of the interlayer state

Gábor Csányi, P. B. Littlewood, Andriy H. Nevidomskyy, C. J. Pickard and B. D. Simons

Cavendish Laboratory, Madingley Road, Cambridge CB3 0HE, UK

(Dated: February 2, 2008)

Although not an intrinsic superconductor, it has been long-known that, when intercalated with certain dopants, graphite is capable of exhibiting superconductivity [1]. Of the family of graphite-based materials which are known to superconduct, perhaps the most well-studied are the alkali metal-graphite intercalation compounds (GIC) [2] and, of these, the most easily fabricated is the C_8K system [3] which exhibits a transition temperature $T_c \simeq 0.14\text{ K}$ [2]. By increasing the alkali metal concentration (through high pressure fabrication techniques), the transition temperature has been shown to increase to as much as 5 K in C_2Na [4]. Lately, in an important recent development, Weller *et al.* have shown that, at ambient conditions, the intercalated compounds C_6Yb and C_6Ca exhibit superconductivity with transition temperatures $T_c \simeq 6.5\text{ K}$ and 11.5 K respectively [5], in excess of that presently reported for other graphite-based compounds. We explore the architecture of the states near the Fermi level and identify characteristics of the electronic band structure generic to GICs. As expected, we find that charge transfer from the intercalant atoms to the graphene sheets results in the occupation of the π -bands. Yet, remarkably, in all those – and only those – compounds that superconduct, we find that an interlayer state, which is well separated from the carbon sheets, also becomes occupied. We show that the energy of the interlayer band is controlled by a combination of its occupancy and the separation between the carbon layers.

To focus our discussion, we begin with an investigation of the newly discovered C_6Yb system. Our calculations rely on density functional theory (DFT) techniques [6] applied within the local density approximation (LDA) [7]. Since the 4*f*-shell of Yb is found to be filled (in agreement with experiment), the DFT-LDA can be applied with some confidence. Moreover, one may infer that the 4*f*-orbitals play no essential role in superconductivity. The atomic structure of C_6Yb , shown in Figure 1a, involves a stacked arrangement of graphene sheets intercalated with a triangular lattice configuration of Yb atoms. The stacking of the graphene sheets is AAA, while the Yb atoms occupy interlayer sites above the centres of the hexagons of the graphene sheets in an ABAB stacking arrangement leading to a P63/MMC crystallographic structure. We use the same geometry for C_6Ca .

Figure 1d shows the results of the band structure calculation of C_6Yb centered on the Fermi energy. To resolve the qualitative structure of the levels and identify the bands in-

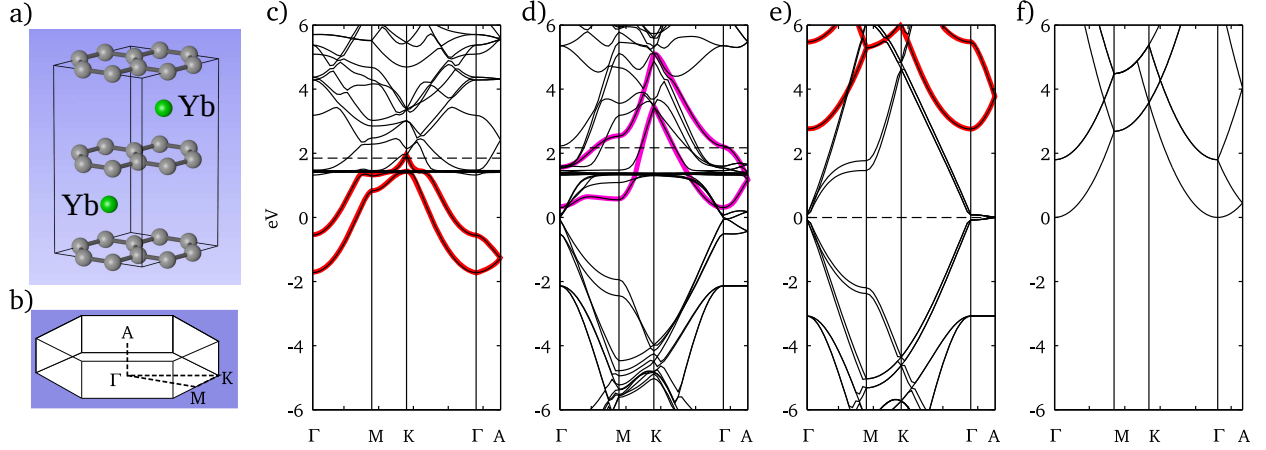


FIG. 1: Band structure of C_6Yb compared to various model systems as inferred from DFT-LDA. The panels correspond to (a) atomic structure and (b) geometry of the Brillouin zone of C_6Yb , band structures of (c) expanded Yb, with the lattice parameters and atomic positions corresponding to those in C_6Yb , so that the nearest Yb-Yb distance is increased by 24% as compared to the pure FCC structure, (d) the C_6Yb compound, (e) the “empty” graphite system, where the Yb atoms have been removed but the lattice constants are kept fixed, and (f) free electron bands, folded into the unit cell of C_6Yb . The free electron-like band is marked with a thick red line, while pink lines indicate hybridized bands with significant charge density in the interlayer region. The band structures (except for the free electron bands) are aligned with respect to the core levels and in each case the Fermi level is shown with a dashed line. Including correlation effects for the localized $4f$ orbitals within the LDA+U method results only in the expected downward rigid shift of the energy of the filled $4f$ levels (not shown).

tersecting the Fermi level, it is helpful to compare the dispersion with the corresponding “empty” graphite-like system and the “empty” Yb metal, obtained by simply removing, respectively, the Yb and carbon atoms from the C_6Yb structure whilst holding the lattice constants fixed. In C_6Yb , the previously unoccupied graphite π^* bands are seen to intersect the new Fermi level (due to the enlarged interlayer distance each are almost doubly degenerate). Of these, one remains almost unperturbed by the presence of Yb while the degeneracy of the other is lifted, and one of the resulting bands strongly hybridizes with a new band that also crosses the Fermi level. The latter resembles both the free electron-like state of expanded Yb metal (panel(c)) and the interlayer band intrinsic to pure graphite (panel (e)). As well as the $5s$ and $5p$ orbitals (which lie well outside the range of energies

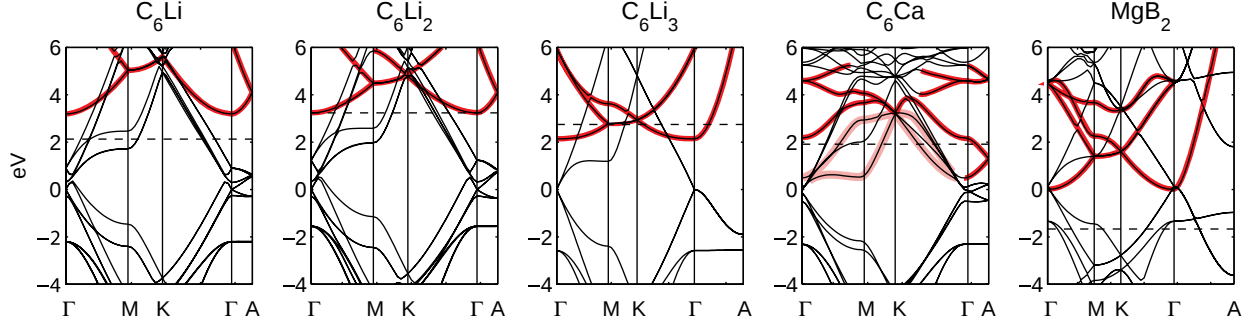


FIG. 2: Band structures of the Li series of GICs, C_6Ca and MgB_2 . The latter is shown in a supercell that matches the others in the plane of the graphene sheets. The interlayer band is marked with a thick red line, while pink lines indicate hybridized bands with significant charge density in the interlayer region. The band structures are aligned by the crossing of the π bands, in each case the Fermi level is shown with a dashed line.

shown in Figure 1d), the 2×7 $4f$ orbitals associated with the two Yb atoms in the unit cell form a set of localized almost non-dispersive bands which appear at ca. 0.8 eV below the Fermi level. Referring to Figure 2 (panel 4), and the discussion in Ref. [8], we note that a similar phenomenology applies to the band structure of C_6Ca .

Although the presence of the interlayer band and its hybridisation with the π^* band helps to explain the diminished normal state resistance anisotropy observed in C_6Yb over that of pure graphite [5], could its occupation be significant for superconductivity? To address this question, it is instructive to draw comparison with other superconducting GICs. It is known from LEELS measurements of the superconducting compound C_8K that, in common with the C_6Yb system, the interlayer band lies below the Fermi energy [9]. However, a more discerning test of the significance of the interlayer state is presented by the Li intercalates. While intercalation at ambient pressure leads to the C_6Li structure, high pressure techniques can be used to fabricate C_3Li and C_2Li compounds. Significantly, while the C_3Li system remains (like its cousin C_6Li) non-superconducting, C_2Li exhibits a transition with a $T_c \simeq 1.9$ K [10]. Referring to Figures 2 and 3, one may note that, in common with the C_6Yb and C_6Ca system, the Li GICs also exhibit a free electron-like interlayer band. The dispersive character of this band is reflected clearly in the Fermi surface (see Fig. 3a). However, significantly, increasing Li ion concentration (and, with it, the degree of electron doping) leads to a lowering of the interlayer band resulting in its occupancy in the C_2Li system. Indeed,

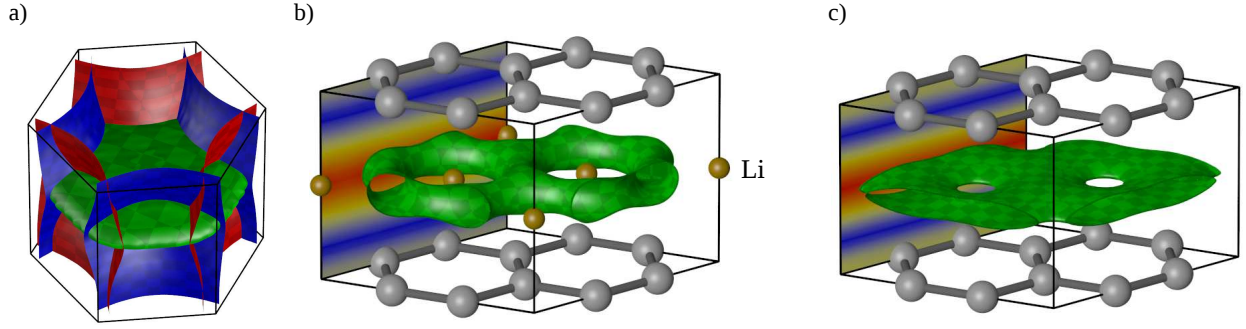


FIG. 3: Structure of the interlayer state. (a) Fermi surface of the C_2Li system as inferred from the band structure calculation. In its native state, the Fermi surface of a single graphene sheet collapses onto two points in the Brillouin zone. Electron-doped, the Fermi surface expands to form a set of two cylindrical electron-like surfaces associated with the π^* bands which enclose the singular points in the spectrum (red and blue). By contrast, the interlayer band, which adopts a nearly free-electron like structure parallel to the planes near the Γ point, acquires a more complex extended character at the Fermi surface (green). (b) An isosurface of the charge density associated with the lowest interlayer band in C_2Li at the Γ point. The colourmap on the left plane shows the projection of the band density, with blue corresponding the low and red to high electron density. The spatial structure of the interlayer band is essentially identical to that of its unoccupied analogue in pure graphite, which is shown in panel (c).

combining the available data in Table I, the coincidence of superconductivity in the GICs with the occupation of the interlayer state is striking.

Studies of the free electron-like interlayer state in pure graphite and GICs have a long history. Although present in early band structure calculations in the pure system, the significance of the (unoccupied) band in graphite and C_6Li was first emphasized by Posternak *et al.* [11, 12] while, subsequently, its existence was confirmed experimentally in both graphite [13] and C_6Li [14]. (The same band has been equivalently referred to as a metallic “sd band” in Ref. [15].) Referring to the Li based GICs, it is apparent that the energy, and therefore also the occupancy, of this band can vary considerably with respect to the other bands present in the above systems.

It is notable that the dispersive $5d$ band of Yb in the expanded metal (Fig. 1c) and the interlayer state in pure graphite (Fig. 1e) both bear strong resemblance to the dispersion

GIC	electron doping	interlayer separation	interlayer band occ.	T_c
graphite	0	3.35Å	no	—
C ₆ Li	1/6	3.7Å	no	—
C ₃ Li	1/3	3.7Å	no	—
C ₂ Li	1/2	3.7Å	yes	1.9K
C ₁₆ K	1/16	5.2Å	no	—
C ₈ K	1/8	5.2Å	yes	0.14K
C ₆ Ca	1/3	4.6Å	yes	11.5K
C ₆ Yb	1/3	4.7Å	yes	6.5K
C ₆ Ba	1/3	5.25Å	yes	?

TABLE I: Table recording the coincidence of the interlayer state occupation in GICs and the phenomenon of superconductivity as inferred from the results of band structure calculation and experiment. According to the electronic structure calculations and the observed phenomenology, one would predict superconductivity in the GIC C₆Ba [16].

of the band of free electrons in the absence of external potential (Fig. 1f). Indeed, we can understand the important features of this nearly free-electron like state by studying the “empty” graphite system with the intercalant ions removed: In Figure 4, we show the effect of charging and layer separation on the energy of the resulting interlayer band. An increase in the c axis lattice constant and in the accumulated charge both lead to a lowering of the band energy, and thus an increase in its occupancy. It is interesting to note that, for a wide range of experimentally known GICs, the interlayer band energy follows closely that of the pure graphite model.

Motivated by preliminary electronic structure calculations, previous theoretical studies by Al Jishi [17, 18] have emphasized the significance of partially occupied two-dimensional graphite π^* bands and three-dimensional interlayer bands for superconductivity. Indeed, these studies have shown that aspects of superconductivity in some GICs can be described well by a two-band phenomenology. Yet the underlying microscopic pairing mechanism remains in question. Significantly, unlike the fullerene-based superconducting compounds,

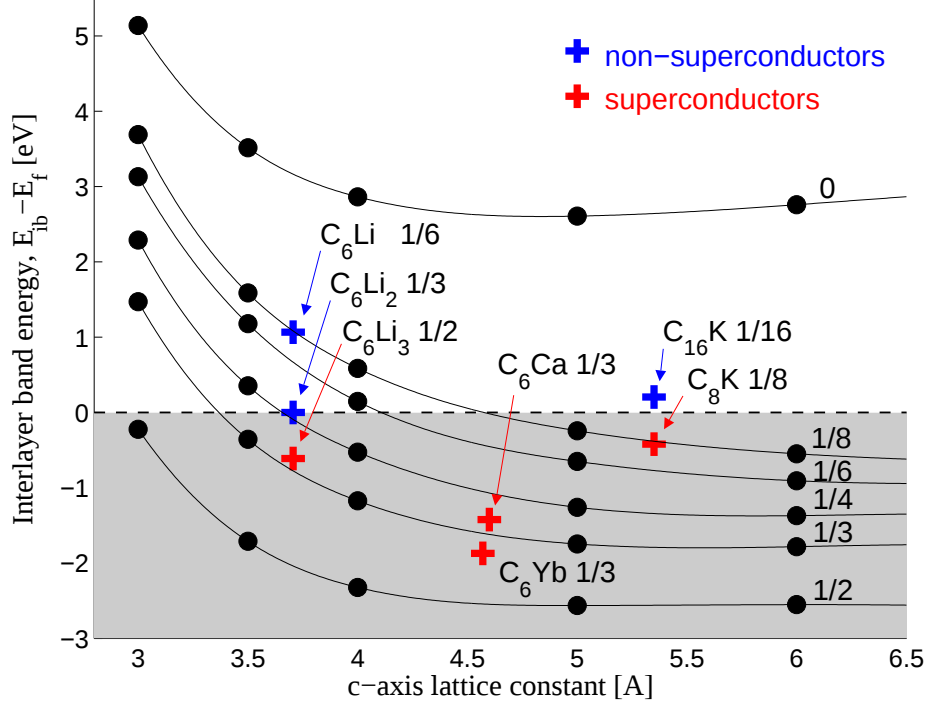


FIG. 4: The dependence of the interlayer band energy (at the Γ point) of the empty graphite system with changing c axis spacing for different electron dopings. (Note that the calculation of the electron doped system using periodic boundary conditions requires overall charge neutrality, enforced by a uniform positive background charge.) Superposed on the figure are data points corresponding to different GICs, red and blue crosses indicate whether the compound is found to be superconducting or not, respectively. The fractions show the electron doping of the graphite sheets in units of electron per carbon atom. In the systems that fall into the shaded area, the interlayer band is occupied.

the π^* bands are decoupled from the out-of-plane lattice vibrations of the graphene sheets, and couple only weakly to the in-plane modes. By contrast, one may expect the interlayer band to engage with lattice vibrations of the metal ions and, through their hybridisation with the π^* bands, the graphene sheets. Indeed, recent numerical calculations by Calandra and Mauri have revealed the presence of strong electron-phonon coupling in C_6Ca , facilitated by the occupation of the free-electron like band [8]. Whether an electron-phonon mechanism alone can explain the broad distribution of T_c observed across the range of GICs, as well as the staging dependence [19], remains a question for future investigation. In this context, it is interesting to note that, in those compounds with a low transition temperature, the

interlayer band remains nearly orthogonal to the π^* bands, as it is in pure graphite, while in C_6Yb and C_6Ca the hybridization is strong.

Intriguingly, through its weak coupling with the graphene layer, one may expect occupancy of the intrinsic interlayer band of graphite to provide an ideal environment for soft charge fluctuations that could promote (*s*-wave) superconductivity via an excitonic pairing mechanism [20]. Indeed, the same weak coupling diminishes the potential for charge density wave instability which might otherwise compete with the superconducting pair correlations. In this context, it is interesting to note that a parallel pairing mechanism involving the exchange of acoustic plasmons was suggested by Takada [21] and was much discussed after the discovery of superconductivity in the cuprates. Recently, the model has been re-evaluated for layered metals [22]. Bearing in mind that low-frequency plasma oscillations will, of course, couple to the ionic positions—conventional acoustic phonons can be viewed as simply coupled ionic and electronic plasma oscillations—such processes present an effective mechanism to enhance electron–phonon coupling.

Recognizing the auspicious role played by the free-electron like state in the superconducting GICs, it is tempting to look for a common phenomenology in the isoelectronic family of boron intercalates and, in particular, the well-studied superconducting compound MgB_2 which exhibits a transition temperature $T_c = 39\text{K}$ [23]. Although the material indeed possesses interlayer states, the band structure (Fig. 2) shows that it remains unoccupied. However, in contrast to C_6Yb and the other superconducting GICs, in this case charge carriers are transferred from the σ to the π^* band. The resulting band of hole-like σ states couples strongly to the host lattice providing a natural environment to realise a high temperature phonon-mediated superconductivity.

Finally, it is interesting to note that the interlayer states find their analogue as nearly free-electron like states in the carbon nanotube system: early theoretical [24] and experimental [25] investigations of the alkali-metal nanotube intercalates already indicate a phenomenology in doping dependence similar to the GICs. On this background, an investigation of possible superconductivity in electron-doped carbon nanotubes would seem to be a timely and worthwhile enterprise.

Methods: The results reported here were obtained from an implementation of the LDA within the framework of the Castep package [26]. The methodology, which includes the use of ultrasoft pseudopotentials, has been validated in many environments including the rare

earth compounds [27]. Here, we take advantage of the fact that, in using ultrasoft pseudopotentials, one can exercise a considerable degree of freedom in deciding which electron shells to treat as fixed core and which to treat as valence, free to participate in bonding.

The numerical results presented for C_6Yb were computed treating all the electrons below the 5s level for Yb, and below the 2s level for carbon atoms as core, respectively. Plane waves up to 480 eV were used to expand the electronic states, and the Brillouin zone was sampled with a $12 \times 12 \times 6$ mesh. (A test calculation using a 600 eV cutoff did not yield appreciably different results.) To check for possible correlation effects, we used the LDA+U method as implemented in the PWSCF package [28] with U varying between 3 and 7 eV.

-
- [1] M. S. Dresselhaus and G. Dresselhaus, *Intercalation compounds of graphite*, Adv. in Phys. **51**, 1–186 (2002).
 - [2] Y. Koike, H. Suemetsu, K. Higuchi, and S. Tanuma, *Superconductivity in graphite–alkali metal intercalation compounds*, Physica B+C, **99**, 503–508 (1980).
 - [3] N. B. Hannay *et al.*, *Superconductivity in graphite compounds*, Phys. Rev. Lett. **14**, 225–226 (1965).
 - [4] I. T. Belash, A. D. Bronnikov, O. V. Zharikov and A. V. Palnichenko, *On the superconductivity of graphite intercalation compounds with sodium* Solid State Commun. **64**, 1445–1447 (1987).
 - [5] T. Weller, M. Ellerby, S. S. Saxena, R. Smith and N. Skipper, *Superconductivity in the intercalated graphite compounds C_6Yb and C_6Ca* , Nature Physics, to appear.
 - [6] M.C. Payne, M. P. Teter, D. C. Allan, T. A. Arias and J. D. Joannopoulos, *Iterative minimization techniques for ab initio total-energy calculations: molecular dynamics and conjugate gradients*, Rev. Mod. Phys. **64**, 1045–1097 (1992).
 - [7] J. Perdew and A. Zunger, *Self-interaction correction to density-functional approximations for many-electron systems*, Phys. Rev. B **23**, 5048–5079 (1981).
 - [8] M. Calandra and F. Mauri, cond-mat/0506082
 - [9] A. Koma, K. Miki, H. Suematsu, T. Ohno, and H. Kamimura, *Density-of-states investigation of C_8K and occurrence of the interlayer band*, Phys. Rev. B **34**, 2434–2438 (1986).
 - [10] I. T. Belash, A. D. Bronnikov, O. V. Zharikov and A. V. Pal’nichenko, *Superconductivity of graphite intercalation compound with lithium C_2Li* , Solid State Commun. **69**, 921–923 (1989).

- [11] M. Posternak, A. Baldereschi, A. J. Freeman, E. Wimmer, and M. Weinert, *Prediction of Electronic Interlayer States in Graphite and Reinterpretation of Alkali Bands in Graphite Intercalation Compounds*, Phys. Rev. Lett. **50** 761–764 (1983).
- [12] N. A. W. Holzwarth, S. G. Louie, and S. Rabii, *Interlayer states in graphite and in alkali-metal-graphite intercalation compounds*, Phys. Rev. B **30**, 2219–2222 (1984).
- [13] B. Reihl, J. K. Gimzewski, J. M. Nicholls, and E. Tosatti, *Unoccupied electronic states of graphite as probed by inverse-photoemission and tunneling spectroscopy*, Phys. Rev. B **33**, 5770–5773 (1986).
- [14] Th. Fauster, F. J. Himpsel, J. E. Fischer, and E. W. Plummer, *Three-Dimensional Energy Band in Graphite and Lithium-Intercalated Graphite*, Phys. Rev. Lett. **51**, 430–433 (1983).
- [15] S. L. Molodtsov, C. Laubschat, M. Richter, Th. Gantz, and A. M. Shikin, *Electronic structure of Eu and Yb graphite intercalation compounds*, Phys. Rev. B **53**, 16621–16630 (1996).
- [16] The structural of C₆Ba has been reported in: A. Hérol, *Crystallo-chemistry of carbon intercalation compounds*, in *Intercalated Materials*, edited by F. Lévy (D. Reidel Publishing Company, Dordrecht, Holland, 1979), p.335; D. Guérard, A. Hérol, C.R. Acad. Sc. Paris, 1974, Série C, **279**, 455.
- [17] R. Al Jishi, *Model for superconductivity in graphite intercalation compounds*, Phys. Rev. B **28**, 112–116 (1983);
- [18] R. A. Jishi and M. S. Dresselhaus, *Superconductivity in graphite intercalation compounds*, Phys. Rev. B **45**, 12465–12469 (1992).
- [19] Y. Iye and S. Tanuma, *Superconductivity of graphite intercalation compounds with alkali-metal amalgams*, Phys. Rev. B **25**, 4583–4592 (1982).
- [20] D. Allender, J. Bray and J. Bardeen, *Model for an exciton mechanism of superconductivity*, Phys. Rev. B **7**, 1020–1029 (1973).
- [21] Y. Takada, *Plasmon Mechanism of Superconductivity in Two- and Three-Dimensional Electron Systems*, J. Phys. Soc. Jpn. **45**, 786–794 (1978).
- [22] For a recent evaluation of the models, see A. Bill, H. Morawitz, and V. Z. Kresin *Electronic collective modes and superconductivity in layered conductors*, Phys. Rev. B **68**, 144519 (2003)
- [23] J. Nagamatsu, N. Nakagawa, T. Muranaka, Y. Zenitani and J. Akimitsu, *Superconductivity at 39 K in magnesium diboride*, Nature (London) **410**, 63–64 (2001).
- [24] Y. Miyamoto, A. Rubio, X. Blase, M. L. Cohen and S. G. Louie, *Ionic cohesion and electron*

- doping of thin carbon tubules with alkali atoms*, Phys. Rev. Lett. **74**, 2993–2996 (1995).
- [25] H. Shimoda, B. Gao, X. P. Tang, A. Kleinhammes, L. Fleming, Y. Wu and O. Zhou, *Lithium intercalation into opened single-wall carbon nanotubes: Storage capacity and electronic properties*, Phys. Rev. Lett. **88**, 015502 (2002).
- [26] M. D. Segall, Philip J D Lindan, M J Probert, C J Pickard, P J Hasnip, S J Clark and M C Payne, *First-principles simulation: ideas, illustrations and the CASTEP code* J. Phys. Cond. Matt. **14** 2717–2744 (2002).
- [27] C. J. Pickard, B. Winkler, R. K. Chen, M. C. Payne, M. H. Lee, J. S. Lin, J. A. White, V. Milman and D. Vanderbilt, *Structural Properties of Lanthanide and Actinide Compounds within the Plane Wave Pseudopotential Approach*, Phys. Rev. Lett. **85**, 5122–5125 (2000).
- [28] S. Baroni, A. Dal Corso, S. de Gironcoli, and P. Giannozzi, <http://www.pwscf.org>

ACKNOWLEDGEMENTS: We are grateful to S. S. Saxena and Mark Ellerby for bringing the C_6Yb and C_6Ca compounds to our attention and to Gil Lonzarich for contributing to our understanding.